

# An Experimental Study on Mechanical Properties of E-Plastic Waste Concrete

Sai Venu Madhav.H

Post Graduate Student, Civil Engineering, Prasad Engineering College, Telangana, India

\*\*\*

**Abstract** *This paper seeks to optimize the benefits of using E-Plastic Waste in the fiber form in concrete. The E -Plastic Waste is shredded into fibers of specific shapes and sizes. Several design concrete mixes with various proportions of waste plastic fibers for three aspect ratios are prepared and casted as per requirements of the test into the respective moulds. Curing was done for 7,14 and 28 days. Tests were conducted to find out the workability, compressive strength, split tensile and flexural strength. The results were compared with control concrete. It is observed that with the addition of E Plastic for 4cm and 3cm is added, the compressive strength gets increased up to a maximum of 5.9% and 10.6% respectively when compared with the compressive strength of the conventional concrete. The improvement in mechanical properties of concrete was observed. The behavior of plastic incorporated concrete depending on sizes of fibers is resulted in this paper.*

**Key Words:** Solid Waste, E Plastic waste Fiber

## 1. INTRODUCTION

E waste describes loosely discarded, surplus, obsolete, broken, electrical or electronic devices. Rapid technology change, low initial cost have resulted in a fast growing surplus of electronic waste around the globe. Several tones of E waste need to be disposed per year. Traditional landfill or stockpile method is not an environmental friendly solution and the disposal process is also very difficult to meet EPA regulations. How to reuse the non-disposable E waste becomes an important topic to be discussed.

## 2. PLASTICS WITH CONCRETE

The plastic is one of the recent engineering materials which have appeared in the market all over the world. Plastics were used in bath and sink units, corrugated and plain sheets, floor tiles, joint less flooring, paints and varnishes and wall tiles. Other than these, domestically plastics were used in various forms as carry bags, bottles, cans and also in various medical utilities. There has been a steep rise in the production of plastics from a mere 30 million kN in 1955, it has touched 1000 million kN at present. It is estimated that on an average 25% of the total plastic production in the world is used by the building

industry. The per capita consumption of plastics in the developed countries ranges from 500 to 1000 N while in India, it is only about 2 N. There is however now increase in awareness regarding the utilization of plastic as a useful building material in India. Plastics are normally stable and not biodegradable. So, their disposal poses problems. Research works are going on in making use of plastics wastes effectively as additives in bitumen mixes for the road pavements. Reengineered plastics are used for solving the solid waste management problems to great extent. This study attempts to give a contribution to the effective use of waste plastics in concrete in order to prevent the ecological and environmental strains caused by them, also to limit the high amount of environmental degradation.

## 2.1 Plastic Waste-Copper Wire Insulation

Polyvinyl Chloride (PVC) wire insulations as seen in fig 1 are used as an admixture in the concrete. The insulations are acquired from various scrap vendors. PVC is a major plastics material which finds widespread use in building, transport, packaging, electrical/electronic and healthcare applications.



Fig -1: Pvc Copper Wire Insulation with 4mm diameter

## 2.2 Properties of E Plastic waste

Properties of E Plastic waste is tabulated in table 1

**Table -1:** Properties of Material Used

Physical Properties	
Diameter of wire	4mm
Thickness of insulation	0.8 mm
Tensile Strength Notched	2.60 N/mm <sup>2</sup>
Impact Strength	2.0 - 45 kJ/m <sup>2</sup>
Max Cont Use Temp	60 <sup>0</sup> C
Density	1.38 g/cm <sup>3</sup>

## 3. OBJECTIVE OF THE STUDY

- To present a comparative study on the Mechanical and Physical properties of E-Plastic waste incorporated concrete.
- To reuse & improve the efficiency of utilizing the E-Plastic waste particles as a concrete constituent, thereby objective lies in E-Plastic waste Management.

## 4. METHODOLOGY

Preliminary tests are carried as per IS standard on the material used for concrete like specific gravity, fineness, consistency, and initial setting time for cement. For fine and coarse aggregates tests such as sieve analysis, specific gravity, impact value, crushing value are conducted as per standard and results are tabulated.

Based on the results of the materials the mix design is prepared and the casting is done for conventional concrete and the tests are to be done on hardened concrete. Based on the same mix design, concrete with E-Plastic waste incorporated in it is casted and the test results are to be found from the hardened concrete.

The addition of plastics will be based on the results of the trial mixes that will ensure the confirmation of the perfect aspect ratio and the volume to be used. After the confirmation of aspect ratio, the casting of specimen will be done accordingly followed by the strength tests. The design mixes will be prepared and different specimens will be casted and later on tested after that the results will be drawn and concluded.

**Table -2:** Mix Proportions

Water	Cement	Fine Aggregate	Coarse Aggregate
188.79	377.58	495	1171

0.5	1	1.31	3.10
-----	---	------	------

From above table the mix ratio is 1:1.31:3.10

## 5. EXPERIMENTAL PROGRAMME

The main aim of this paper is to study the mechanical related properties of concrete with different proportions of materials and to compare them.

### 5.1 Materials used in the present work

The materials used in the present investigation are;

- Cement – OPC 53 grade conforming to IS 12269 – 1987
- Fine aggregate – natural sand – IS383 – 1970
- Coarse aggregate–crushed 20mm maximum size– IS383–1970
- E Plastic waste material (wire insulations)
- Portable water

### 5.2 Tests on materials

The various types of tests were conducted on cement, fine aggregate and coarse aggregate and the results are tabulated in table 3, table 4 and table 5 respectively. The table 3 below shows the different types of tests carried out on cement.

**Table -3:** Test on Cement

Tests	Results
Specific Gravity	2.54
Fineness	97.33%
Consistency	31%
Initial Setting Time	34 min

The table 4 below shows the different types of tests carried out on fine aggregate.

**Table -4:**Test on Fine Aggregate

Tests	Results
Specific Gravity	2.73
Free Surface Moisture	2%
Gradation	Zone II

The table 5 below shows the different types of tests carried out on coarse aggregate.

**Table -5:**Test on Coarse Aggregate

Test	Results
Specific Gravity	2.78

Aggregate Impact Value	32.73%
Aggregate Crushing Values	18.90%

A total of 13 mixes of concrete with different proportion of E Plastic waste (0%, 0.4%, 0.6%, 0.8 % and 1%) were prepared as shown in table 6 on which the experimental investigation was carried out.

**Table -6:**Mix Proportions

Mix	Proportion
Mix1	OPC+FA+CA
Mix2	OPC+FA +CA+ 0.4%plasticmaterial (size5cm)
Mix3	OPC+FA +CA+ 0.6%PlasticMaterial(size5cm)
Mix4	OPC+FA +CA+ 0.8%PlasticMaterial(size5cm)
Mix5	OPC+FA+CA + 1%PlasticMaterial(size5cm)
Mix6	OPC+FA+CA+ 0.4%PlasticMaterial(size4cm)
Mix7	OPC+FA+CA+ 0.6%PlasticMaterial(size4cm)
Mix8	OPC+FA+CA+ 0.8%PlasticMaterial(size4cm)
Mix9	OPC+FA+CA + 1%PlasticMaterial(size4cm)
Mix10	OPC+FA+CA+ 0.4%PlasticMaterial(size3cm)
Mix11	OPC+FA+CA+ 0.6%PlasticMaterial(size3cm)
Mix12	OPC+FA+CA+ 0.8%PlasticMaterial(size3cm)
Mix13	OPC+FA+CA+ 1%PlasticMaterial(size3cm)

OPC: Ordinary Portland cement

FA: Fine aggregate

CA: Coarse aggregate

The plastic material is shredded into small pieces of 5cm, 4cm, and 3cm and is used accordingly.

### 5.3 Tests on fresh concrete

The tests conducted on fresh concrete are shown below in table 7

**Table -7:** Tests on Fresh Concrete

Tests	Results
Slump	17mm
Compacting Factor	0.9

### 5.4 Tests on hardened concrete

#### 5.4.1 Compressive Strength Test

The compression test on hardened concrete was conducted as shown in fig. 2 and the results are tabulated in table 8




**Fig -2:** Compressive strength test on concrete cube

The table 8 below gives the compressive strength of cubes for 7 days, 14 days and 28 days for all mixes.

**Table -8:** Compression Test on Concrete Cubes


Mix	Compressive Strength, N/mm <sup>2</sup> (7days)	Compressive Strength, N/mm <sup>2</sup> (14days)	Compressive Strength, N/mm <sup>2</sup> (28days)
1	21.3	27.3	30.1
2	22.5	28.2	31.2
3	20.7	27.2	30.3
4	20.5	26.5	30.01
5	19.3	25.9	29.3
6	22.9	27.8	31.2
7	23.6	28.3	31.8
8	23.3	28.9	31.9
9	20.8	26.9	30.8
10	27.7	27.7	30.5
11	22.5	27.9	31.9
12	21.5	28.7	32.2
13	20.9	28.9	33.3

The Chart-1 below shows the compressive strength of concrete cubes with 5cm plastic materials incorporated in it with different proportions for 7 days, 14 days and 28 days of curing.

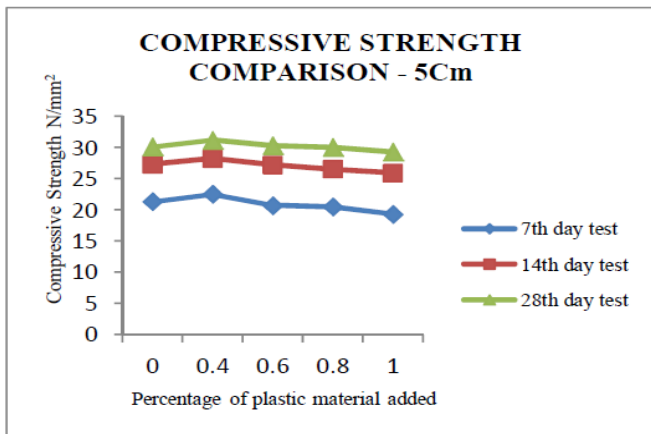


**Chart -1:** Shows the Compressive strength of Concrete cubes with 5cm plastic fiber

The chart-2 below shows the compressive strength of concrete cubes with 4cm plastic materials incorporated in it with different proportions for 7 days, 14 days and 28 days of curing.

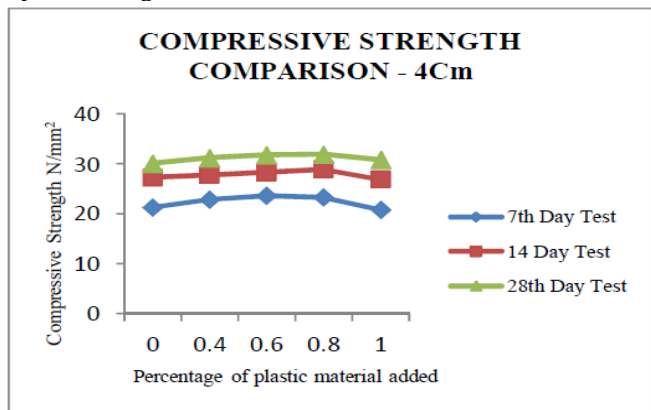

**Chart -2:** Shows the Compressive strength of Concrete cubes with 4cm plastic fiber

The chart-3 below shows the compressive strength of concrete cubes with 3cm plastic materials incorporated in it with different proportions for 7 days, 14 days and 28 days of curing.

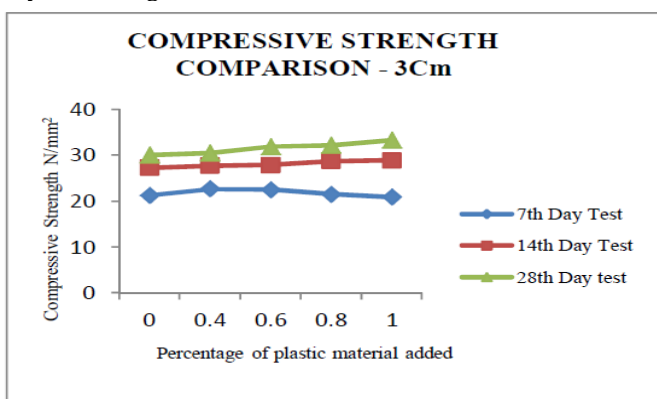

**Chart -3:** Shows the Compressive strength of Concrete cubes with 3cm plastic fiber

### 5.4.2 Tensile Strength Test

The Tensile test on hardened concrete was conducted as shown in fig. 3 and the results are tabulated in table 9. The table 9 below gives the tensile strength of cubes for 7 days, 14 days and 28 days for all mixes.





**Fig -3:** Tensile strength test on concrete cylinders

**Table -9:** Tensile Test on Concrete Cylinders

Mix	Tensile Strength, N/mm <sup>2</sup>	Tensile Strength, N/mm <sup>2</sup>	Tensile Strength, N/mm <sup>2</sup>
1	2.4	2.88	3.44
2	2.42	2.92	3.46
3	2.46	2.9	3.48
4	2.56	2.98	3.5
5	2.3	2.86	3.52
6	2.5	2.96	3.5
7	2.54	2.98	3.52
8	2.48	3	3.58
9	2.46	3.02	3.6
10	2.58	2.92	3.6
11	2.56	2.94	3.58
12	2.52	2.96	3.48
13	2.36	2.82	3.38

The chart-4 below shows the tensile strength of concrete cylinders with 5cm plastic materials incorporated in it with different proportions for 7 days, 14 days and 28 days of curing.

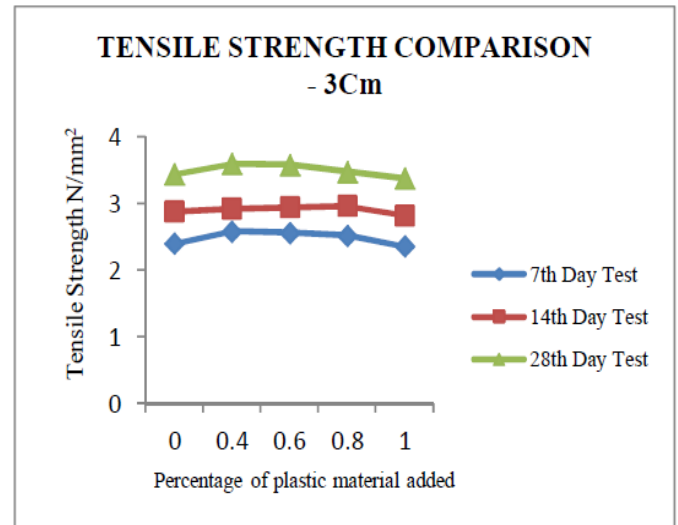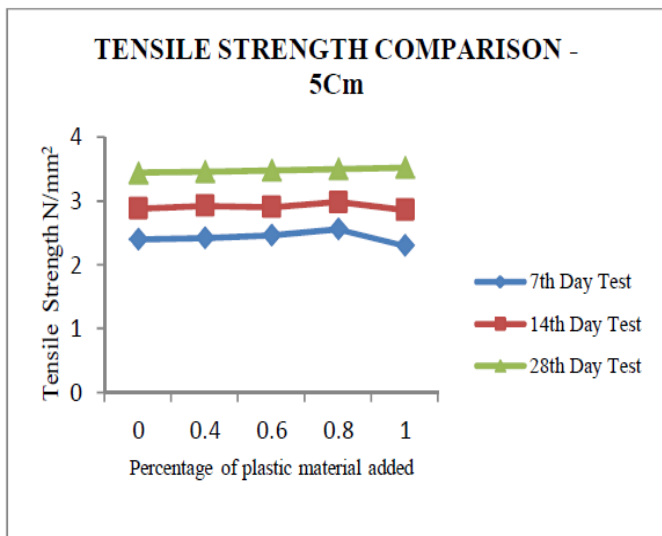


**Chart -4:** Shows the Tensile strength of Concrete cylinders with 5cm plastic fiber

**Chart -6:** Shows the Tensile strength of Concrete cylinders with 3cm plastic fiber

The chart-5 below shows the tensile strength of concrete cylinders with 4cm plastic materials incorporated in it with different proportions for 7 days, 14 days and 28 days of curing.

**5.4.3 Flexure Strength Test**

The Flexure test on hardened concrete was conducted as shown in fig-4 and the results are tabulated in table 10.

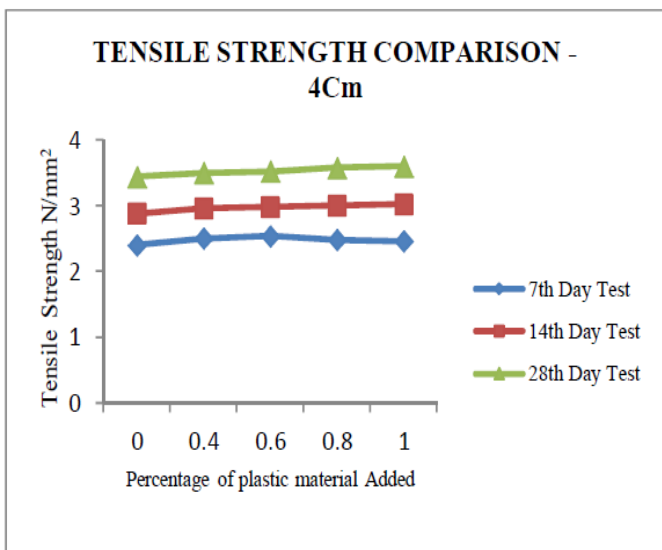

**Chart -5:** Shows the Tensile strength of Concrete cylinders with 4cm plastic fiber

The chart-6 below shows the tensile strength of concrete cylinder with 3cm plastic materials incorporated in it with different proportions for 7 days, 14 days and 28 days of curing.




**Fig -4:** Flexure Strength test on concrete beam

**Table -10:** Flexure Test on Concrete Beams

EPlastic material size	Flexure Strength, N/mm <sup>2</sup> (28days)				
	0%	0.4%	0.6%	0.8%	1.0%
5cm	4.5	6	6.5	5.5	5
4cm	4.5	5	5.5	6	5
3cm	4.5	5	6	6.5	7

The chart-7 below shows the Flexure strength of concrete beams with 5cm, 4cm and 3cm plastic materials incorporated in it with different proportions for 28 days of curing.

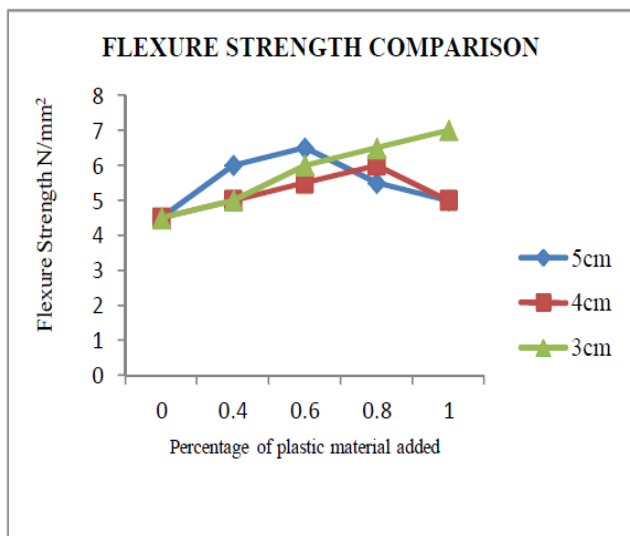

**Chart -7:** Shows the Flexure strength of Concrete Beams

## 6. CONCLUSIONS

It has been confirmed that no major changes are found in the compressive strength of concrete with the presence of E-plastic. However when 1% of the E-plastic for 5cm is added, the compressive strength gets reduced by 2.59 % when compared to control mix. With addition of the E-plastic - 4cm and E-plastic - 3cm the compressive strength gets increased up to a maximum of 5.9 % and 10.6% respectively when compared to control mix.

It has been confirmed that increase in strength is found in the tensile strength of concrete with the presence of E-plastic. When 1% of the E-plastic for 5cm is added, the tensile strength gets increased by 2.3% and for 1% of 4cm; the strength increase observed is 4.6% when compared to control mix at 28 days of curing. However when 1% of the E-plastic for 3cm is added, the tensile strength initially gets increased by 4.6% and then gets decreased with increase in percentage.

It has been confirmed that increase in strength is found in the Flexure strength of concrete with the presence of E-plastic. When E-plastic for 5cm and 4cm is added, the flexure strength gets increased up to 44.4 % and 33.3% respectively. The max strength increase is being observed while using E Plastic waste shredded into

size of 3cm where in total increase of 55.5% is being observed.

## REFERENCES

- [1] R. N. Nibudey et. al., "Strength And Fracture Properties Of Post Consumed Waste Plastic Fiber Reinforced Concrete" International Journal of Civil, Structural, Environmental and Infrastructure Engineering Research and Development (IJCSEIERD) ISSN 2249-6866, Vol. 3, Issue 2, Jun 2013, 9-16.
- [2] R.Lakshmi, S. Nagan , "Investigations On Durability Characteristics Of E-plastic Waste Incorporated Concrete" Asian Journal Of Civil Engineering (Building And Housing) Vol. 12, No. 6 (2011) Pages 773-787.
- [3] R.Lakshmi, S. Nagan, "Utilization of waste E plastic particles in cementitious mixtures" Journal of Structural Engineering, Vol.38, No. 1, April - May 2011, pp. 26-35.
- [4] R. Kandasamy and R. Murugesan, "Fibre Reinforced Concrete Using Domestic Waste Plastics As Fibres" ARPN Journal of Engineering and Applied Sciences, VOL. 6, NO. 3, MARCH 2011
- [5] Indian Standard methods of physical test for hydraulic cement, IS 4031: 1968, Bureau of Indian Standards, New Delhi.
- [6] Indian Standard specification for ordinary and low heat Portland cement, IS 8112: 1989, Bureau of Indian Standards, New Delhi.
- [7] Indian standard methods of tests for aggregates for concrete, IS 2386(Part III), Bureau of Indian Standards, New Delhi.